

सेन्ट्रल इंस्टीट्यूट ऑफ प्लास्टिक्स  
इंजीनियरिंग एंड टेक्नॉलाजी

(रसायन एवं पेट्रोरसायन विभाग,  
रसायन एवं उर्वरक मंत्रालय, भारत सरकार)  
बी-२७, अमौसी इण्डस्ट्रियल एरिया, लखनऊ-२२६ ००८  
फोन: ०५२२-२४३७६४६ फैक्स: ६१-५२२-२४३६२२७  
Email : cipetlko2@gmail.com  
www.cipet.gov.in



एक कदम स्वच्छता की ओर

CENTRAL INSTITUTE OF PLASTICS  
ENGINEERING & TECHNOLOGY

(Deptt. of Chemicals & Petrochemicals  
Ministry of Chemicals & Fertilizers, Govt. of India)  
B-27, Amausi Industrial Area, Lucknow-226 008  
Phone : 0522-2437646 Fax : 91-522-2436227  
Email : cipetlko2@gmail.com  
www.cipet.gov.in

सिपेट/परीक्षण/2018-19/

दिनांक : .....

सेवा में,

To,  
M/s Om Shree Ganesh India (P) Ltd.  
E-61, Bulandshahr Road Industrial Area  
Ghaziabad – 201009 (U.P) INDIA

विषय : Testing of TETTO Colour UPVC Roofing sheet.

आपका पत्रांक : Nil.

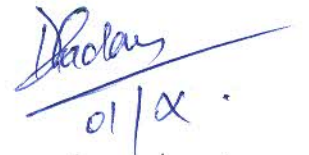
Dated: 23.08.2018

महोदय,

कृपया हमारी परीक्षण रिपोर्ट क्रमांक 0714 प्रमाण पत्र क्रमांक  
E- 0518 बीजक क्रमांक ..... दिनांक ..... प्राप्त करें।

सहयोग के लिए धन्यवाद,

भवदीय

  
01/08

संलग्नक : उपरोक्तानुसार

मुख्य प्रबंधक (तक0सेवा0)

**TEST CERTIFICATE**



**E- 0518**  
Date: 28.09.2018

Issued to: **M/s Om Shree Ganesh India (P) Ltd.**  
**E-61, Bulandshahr Road Industrial Area**  
**Ghaziabad – 201009 (U.P) INDIA**

Your Ref.No. & Date : Nil.

dated : 23.08.2018

TEST REPORT AS PER STANDARD AND AMEND WITH DATE : As per As per requisition.

TEST REPORT NO: 0714

Page 1 of 2

**PART – A :- PARTICULARS OF SAMPLE SUBMITTED**

a)	Name of the sample	:	TETTO Colour UPVC Roofing sheet as stated by party.
b)	Grade / Variety / type / size / class	:	--
c)	Declared value, if any &	:	--
d)	Code No.	:	--
e)	Batch No. & Date of Manufacture	:	--
f)	Quantity	:	Two samples (One corrugated and 1 plain), size 1m X 1m each.
g)	Mode of Packing	:	Packed in woven sack
h)	Sealed or not	:	Not Sealed
i)	Any other information	:	Payment received on 13.08.2018
j)	Date of receipt of sample	:	23.08.2018
k)	Date of starting of testing	:	31.08.2018
l)	Date of completion of testing	:	28.09.2018

**PART - B :- SUPPLEMENTARY INFORMATIONS**

a)	Reference to sampling procedure	:	Not Applicable.
b)	Supporting document for the measurement taken & result derived	:	Not Applicable
c)	Deviation from the test method as prescribed: in relevant work instructions, if any	:	Not Applicable.

**TEST CERTIFICATE**



E - 0518  
Date: 28.09.2018

**PART - C:- TEST RESULTS**

**TEST REPORT No. 0714**

Page 2 of 2

S. No.	Name of the Test	Test Method	Unit	Test Value Obtained
1.	Vicat softening Point	ASTMD- 1525	°C	81.7
2.	Buring/Flammability	IS:11731 (Pt-2)	--	FV <sub>0</sub>
3.	HDT @ 66 PSI	ASTMD- 648	°C	77.4
4.	Water absorption	ASTMD – 570	%	0.08
5.	Izod Impact Strength	ASTMD – 256	KJ/m <sup>2</sup>	93.4
6.	Flexural Modulus	ASTMD- 790	Kg/cm <sup>2</sup>	45838
7.	Flexural Strength			888
8.	Tensile Strength			462.2
9.	Rockwell Hardness	ASTMD – 785	R-scale	82
10.	Density	ASTMD – 792	g/cc	1.58

**PART - D : REMARKS - Nil**

  
**AUTHORIZED SIGNATORY**  
Vivek Kumar  
Technical Manager

  
**AUTHORIZED SIGNATORY**  
D.P. Yadav  
Chief Manager (TS)  
(Quality Manager)

**NOTE :**

- The results relate only to the items tested as supplied by the party.
- The test certificate shall not be reproduced in full except without the written approval of the laboratory.